

AD-A062 017

RUTGERS - THE STATE UNIV PISCATAWAY NJ  
X-RAY HIGH PRESSURE STUDY OF POLYVINYLIDENE FLUORIDE.(U)  
NOV 78 B A NEWMAN, C H YOON, K D PAE  
TR-13

F/G 11/9


N00014-75-C-0540

NL

UNCLASSIFIED

1 OF 1

AD  
A062017



END  
DATE  
FILMED

3--79

DDC

ADA062017

DDC FILE COPY

OFFICE OF NAVAL RESEARCH

Contract N00014-75-C-0540

Task No. NR 356-564

TECHNICAL REPORT, NO. 13

TR-13

X-Ray High Pressure Study of Polyvinylidene Fluoride.


by

B. A. Newman, C. H. Yoon, K. D. Pae

Prepared for Publication

in the

Journal of Materials Science

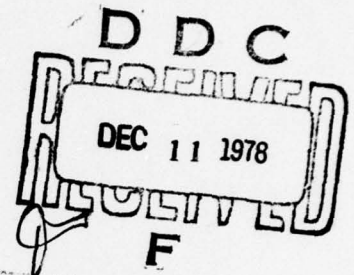

Rutgers University  
High Pressure Research Laboratory  
and  
Department of Mechanics and Materials Science  
P. O. Box 909  
Piscataway, New Jersey 08854

24 November 1978

27p.

Reproduction in whole or in part is permitted for  
any purpose of the United States Government

This document has been approved for public release  
and sale; its distribution is unlimited

410970

Rutgers - The State Univ.,  
Piscataway, NJ

78 12 04 410 970 185 LB

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER Technical Report No. 13	2. GOVT ACCESSION NO.	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) X-RAY HIGH PRESSURE STUDY OF POLY(VINYLLIDENE FLUORIDE)		5. TYPE OF REPORT & PERIOD COVERED Technical Report Interim
		6. PERFORMING ORG. REPORT NUMBER
7. AUTHOR(s) B.A. Newman, C.H. Yoon and K.D. Pae		8. CONTRACT OR GRANT NUMBER(s) N00014-75-C-0540
9. PERFORMING ORGANIZATION NAME AND ADDRESS Rutgers University, High Pressure Research Lab and Dept. of Mechanics & Materials Science, College of Engineering, Piscataway, NJ 08854		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS NR 356-564
11. CONTROLLING OFFICE NAME AND ADDRESS Office of Naval Research (Code 472) Arlington, Virginia 22217		12. REPORT DATE November 20, 1978
		13. NUMBER OF PAGES
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)		15. SECURITY CLASS. (of this report)
		15a. DECLASSIFICATION/DOWNGRADING SCHEDULE
16. DISTRIBUTION STATEMENT (of this Report) Approved for public release; distribution unlimited. Reproduction in whole or in part is permitted for any purpose of the United States Government.		
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)		
18. SUPPLEMENTARY NOTES		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) High Pressure, High Pressure X-Ray Study, Poly(vinylidene fluoride)		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) An x-ray high pressure study at room temperature of both phase I and phase II crystal structures of polyvinylidene fluoride has been carried out. At room temperature both phases are stable up to pressures greater than 14 kbars. The variation of lattice compressive strains with pressure could be fitted to the Tait equation with little scatter and the variation of the unit cell parameters with pressure computed. The bulk lattice compressibilities of both phase I and phase II was found to be considerably less than that of polyethylene with the lowest compressibility being found for the phase I structure. The linear		

DD FORM 1 JAN 73 1473

EDITION OF 1 NOV 68 IS OBSOLETE  
S/N 0102-014-6601

12 04 185

20.

lattice compressibilities are extremely anisotropic with the lowest compressibility being in the chain direction as expected. However, at the highest pressures, for the case of phase II, it was observed that this anisotropy was greatly reduced. Applications of these data to the unique piezoelectric activity of  $\text{PVF}_2$  are pointed out.

ACCESSION for	<input checked="checked" type="checkbox"/> V. to Section	<input type="checkbox"/>
NTIS	<input type="checkbox"/> B. to Section	<input type="checkbox"/>
DDC		
UNANNOUNCED		
JUSTIFICATION		
BY	INFORMATIONAL IDENTITY CODES:	
	P. 1	
A		



X-RAY HIGH PRESSURE STUDY OF POLYVINYLIDENE FLUORIDE

B. A. Newman, C. H. Yoon and K. D. Pae

Rutgers University  
High Pressure Research Laboratory  
and  
Dept. of Mechanics and Materials Science  
Piscataway, New Jersey 08854

## ABSTRACT

An X-ray high pressure study at room temperature of both phase I and phase II crystal structures of polyvinylidene fluoride has been carried out. At room temperature both phases are stable upto pressures greater than 14 kbars. The variation of lattice compressive strains with pressure could be fitted to the Tait equation with little scatter and the variation of the unit cell parameters with pressure computed. The bulk lattice compressibilities of both phase I and phase II was found to be considerably less than that of polyethylene with the lowest compressibility being found for the phase I structure. The linear lattice compressibilities are extremely anisotropic with the lowest compressibility being in the chain direction as expected. However, at the highest pressures, for the case of phase II, it was observed that this anisotropy was greatly reduced.

Applications of these data to the unique piezo-electric activity of  $\text{PVF}_2$  are pointed out.

## INTRODUCTION

In recent years, high pressure X-ray studies of several polymers have been carried out by various workers. An investigation of polyethylene at room temperature at pressures up to 4 kbar was made by Ito<sup>(1)</sup>. A phase transition occurring in polytetrafluoroethylene at room temperature and 7.2 kbar was studied by Flack<sup>(2)</sup>. The crystallization of polyethylene under conditions of high pressure at high temperatures was investigated by Bassett, Piermarini and Block<sup>(3)</sup> using X-ray methods. In this laboratory high pressure studies of polyethylene<sup>(4,5)</sup> and nylon 11<sup>(6)</sup> at room temperature and at elevated temperatures has been made. An X-ray study of the crystallization of polyethylene at high pressures has also been made by Yasuniwa, Enoshita, and Takemura<sup>(7)</sup>. A recent review of X-ray high pressure studies of polymers has been made by Ito<sup>(8)</sup>.

Crystallization studies of polyvinylidene fluoride (PVF<sub>2</sub>) at high pressures and temperatures have been carried out by several investigators. Doll and Lando showed that pressure crystallization of PVF<sub>2</sub> gave rise to a new X-ray pattern which they designated as phase III, but later they demonstrated that this phase was a mixture of phase I and phase II<sup>(9,10)</sup>. The effect of heat treatments at high pressure on the three crystalline forms of PVF<sub>2</sub> was studied by Hasegawa, Kobayashi and Tadokoro<sup>(11)</sup> who concluded that phase II was the most stable at room pressure, phase I was formed under special conditions, while phase III was an intermediate modification between I and II. On the other hand a third crystal phase, phase III was reported by Hasegawa, Takahashi, Chatani and Tadokoro<sup>(12)</sup> to be obtained by casting from a solution of dimethyl sulfoxide. Heating of unoriented phase II under high pressure gave rise to a mixture of phase I and phase III. More recently a study of melting and crystallization under high pressure has been made by Matsushige and Takemura<sup>(13)</sup> using a high pressure



D.T.A. cell.

The question of the relative stabilities of phases I, II and III appears to be unsettled at the present time. Investigations at atmospheric pressure, of samples subjected to various heat treatments and pressures, do not elucidate crystal structures present at high pressures without ambiguity, since reversible solid-state phase transitions may occur with increasing or decreasing pressure and have been reported for other polymers<sup>(2,3,5,6,7)</sup>. Moreover, studies with a high pressure D.T.A. cell at this laboratory do not confirm in all respects the study of Matsushige and Takemura<sup>(13)</sup>. Unambiguous phase determination at high pressure can only be made using high pressure X-ray techniques.

PVF<sub>2</sub> is also interesting from the stand-point of its unusual piezo-electric activity. The mechanism for the piezoelectricity and pyroelectricity observed in poled films of oriented phase I PVF<sub>2</sub> is not completely understood at the present time, but it now appears probable that dipole orientation in crystallites is most important. If the piezoelectric effect arises from changes in dipole moment per unit volume caused by lattice compression, then the magnitude of the piezoelectric coefficient should be directly related to the lattice compressibility. High pressure X-ray diffraction can be used to measure lattice compressibility at different pressures and temperatures.

For these reasons PVF<sub>2</sub> has been studied both at room temperature and at higher temperatures using high pressure X-ray methods. These data have been supplemented with high-pressure quenching crystallization experiments and high pressure D.T.A. studies. Here the results obtained using high pressure X-ray methods at room temperature are presented. Both phase I and phase II crystal structures were studied.



## EXPERIMENTAL

### (a) Sample Preparation.

Capacitor grade Kureha KF-film was obtained from Kureha Chemical Industries Co. Ltd., Japan. To prepare unoriented samples with phase II crystal structures, the film was melted and slowly cooled to room temperature. The resulting film was annealed at 120° C for one hour. To prepare samples of phase I crystal structure the film was drawn at 50° C to a draw ratio of ~5:1.

### (b) X-ray diffraction high pressure camera.

A high pressure X-ray diffraction camera designed and constructed in this laboratory and based on the diamond piston-anvil method was used. The sample was contained by a gasket, and surrounded with silicone oil so that a hydrostatic pressure on the sample was generated. The sample was mixed with hexamethylene tetramine (H.M.T.) which could be used as an internal standard to determine the applied pressure<sup>(14)</sup>. Filtered molybdenum radiation was used from a Rigaku-Denki rotating anode 6.3 KW X-ray generator. X-ray patterns were recorded on flat film. The film to specimen distance was determined from the X-ray diffraction from the H.M.T. at atmospheric pressure.

### (c) Phase II crystal lattice

A typical X-ray diffraction pattern taken at ~5Kbars of a phase II sample is shown in figure 1. The sample is unoriented so that complete Debye-Scherrer rings are obtained. Two rings from H.M.T., (110) and (211), are present together with some lines determined as originating from the gasket material. Large Laue spots from the diamond crystals are also evident. Three strong reflections (110), (021), and (002) from  $\text{PVF}_2$  can be seen together with a fourth strong reflection (020) partially obscured by the (110) reflection from H.M.T. A sample containing no H.M.T. was studied and the (020) reflection was easily observed.

According to Hasagawa, Takahashi, Chatani and Tadokoro<sup>(12)</sup>, phase II is monoclinic but pseudo-orthorhombic  $a=4.96\text{\AA}$ ,  $b=9.64\text{\AA}$ ,  $c=4.62\text{\AA}$  and  $\beta=90^\circ$ . No indication that the structure should be considered as monoclinic is indicated from the lattice, which is orthorhombic to within the experimental accuracy of the data. The space group cannot be assigned with complete confidence at the present time and both monoclinic and triclinic space groups are possible. Tadokoro and co-workers suggest the space-group  $P2_1/c$  ( $C_{2h}^5$ ) which is monoclinic.

The procedure adopted was to take a large number of X-ray diffraction photographs at various pressures up to 14.6 Kbars. The pressures were determined to within 0.2 kbar using the reflections from H.M.T. At each pressure the unit cell dimensions were determined from the d-spacings of (110), (021) and (002) reflections, assuming lattice orthogonality remained at higher pressures. Two separate sequences of measurements were made on two different samples to obtain a large number of data, to provide an indication of the actual scatter of data points, and to test for systematic errors.

#### (d) Phase I crystal lattice

Figure 2 shows an X-ray diffraction photograph taken using the oriented phase I sample at approximately 5kbars. Laue reflections from the diamonds, and Debye-Scherrer rings from H.M.T. and gasket material are present as before. Four reflections from the  $PVF_2$  fiber are clearly visible; two equatorial reflections and two first layer line reflections.

Although all reflections from phase I can be indexed on the basis of a hexagonal lattice, Lando, Olf and Peterlin<sup>(15)</sup> have pointed out that space-group  $Cm2m$  considerations indicate that the cell is orthorhombic with a space-group  $Cm2m$  ( $C_{2v}^{14}$ ). Using the orthorhombic cell as a basis for assigning indices, all reflections except (00 $\bar{1}$ ) correspond to at least two different sets of indices.

The four most intense reflections from  $\text{PVF}_2$ , visible on Figure 2 are  $\{(200), (110)\}$ ,  $\{(310), (020)\}$ ,  $\{(111), (201)\}$  and (001). A sequence of photographs was taken at different pressures up to 14.1 kbars, and the d-spacings measured at each pressure level.



## RESULTS

### (a) Phase II

The phase II crystal structure appeared to be stable at room temperature for increasing pressures up to 14.6 Kbars. Figure 3 shows the variation in strains on the (110) and (021) planes for various pressures, all data from different samples being included on the same figure. For purposes of comparison the lattice strain versus pressure variation for the (110) polyethylene lattice planes is shown. The solid lines represent the Tait equation ( $-\epsilon = A \ln(1 + \frac{P}{B})$ ) in the parameters chosen to best fit the data. The best fit parameters obtained were:

for (110)	$A = 0.0138,$	$B = 1.39 \times 10^3 \text{ Kg/cm}^2$
for (021)	$A = 0.0147,$	$B = 3.51 \times 10^3 \text{ Kg/cm}^2$

The Tait equation, with only two adjustable parameters appears to provide an excellent fit of the data. Moreover the data obtained from two completely different samples did not show appreciable differences.

Figure 4 shows the corresponding data for the (002) planes. This data also was fitted to the Tait equation shown by the solid line in figure 4, the parameters obtained being  $A = 0.0645,$   $B = 50.00 \times 10^3 \text{ Kg/cm}^2$ . Since the chain direction is perpendicular to the (002) planes this figure provides an indication of the compressibility of the lattice in the chain direction. It can be seen that the elastic strains are very small (less than 1 % even at pressures above 10 kbars). The corresponding data obtained by Ito<sup>(16)</sup> for polyethylene and polytetrafluoroethylene are also shown. As expected the lower energy chain conformations for polyethylene and polytetrafluoroethylene give rise to a lower compressibility parallel to the chain direction. This would indicate that the greater compressibility for the case of PVF<sub>2</sub> is obtained by incremental bond angle rotations giving rise to a twisting about the chain axis.

The data from figures 3 and 4 enable the lattice parameters a, b and c to be calculated as a function of pressure. The c-parameter can be obtained



directly from (002) planes. If this is known the b-parameter can be calculated from (021) planes. The a-parameter can then be obtained from (110) planes. Figure 5 shows the fractional variation in a and b parameters calculated from the Tait equation parameters. There is very little difference at lower pressures, but above 7 kbars the b-axis appears to show a greater compressibility.

#### (b) Phase I

The phase I crystal structure appears to be stable at room temperature for increasing pressures up to 14.1 Kbars. The changes in d-spacing for the (001) planes were so small even at the highest pressures that they could not be measured with reliability. The values actually obtained are shown in figure 6. The solid lines shown for polyethylene and polytetrafluoroethylene suggest that the compressibility in the chain direction for  $\text{PVF}_2$  is comparable to these polymers. Since the phase I chain conformation is very close to planar zig-zag this would be expected. Certainly the compressibility in the chain direction for phase I is much less than is the case for phase II. The variation in strain with pressure for the other non-equatorial reflection ((111), (201)) is also shown on figure 6. Since strains on these planes also involve strains not perpendicular to the chain axis these strains are also small. The solid line through these points represents the best-fit Tait function with parameters  $A = 0.00506$ ,  $B = 3.68 \times 10^3 \text{ Kg/cm}^2$ .

Changes in the reflections from planes parallel to the chain axis were much larger and are shown in figure 7. If the hexagonal symmetry of the lattice is maintained at higher pressures then lattice compressibilities perpendicular to the chain direction should be isotropic, and this is observed. The solid line represents the best fit Tait function through the data, with parameters  $A = 0.0157$ ,  $B = 3.75 \times 10^3 \text{ Kg/cm}^2$ .

## DISCUSSION

From the Tait equation parameters obtained for both phase I and phase II lattice compressive strains, the variation in unit cell parameters and unit cell volumes with pressure can be calculated. Volumetric data is shown for both phase I and phase II in figure 8 together with the volumetric data for polyethylene. Clearly phase I is considerably less compressible than phase II and both are less compressible than polyethylene. It is known that phase I is a more dense phase than phase II owing to a higher packing efficiency. The greater chain compressibility for the case of phase II has already been discussed. From these considerations the relative compressibilities of the two phases observed in figure 8 would be anticipated.

It is, however, perhaps surprising that polyethylene with the excellent packing efficiency possible with a symmetric molecule, and a low energy all trans planar zig-zag molecular conformation should show a higher volumetric compressibility. The repulsive potential arising from the fluorine atoms may perhaps be responsible for the low volumetric compressibility observed for  $\text{PVF}_2$  compared with polyethylene. In figure 9 the lattice bulk compressibilities for polyethylene phase I and phase II  $\text{PVF}_2$  are shown as a function of pressure and confirm these observations.

In figure 10 the various lattice linear compressibilities for both phase I and phase II are shown. It is interesting to observe that the compressibility of the (110) planes of the phase II structure is the greatest ( $\sim 10 \times 10^{-6} \text{ cm}^2/\text{Kg}$ ) at atmospheric pressure. A very rapid decrease with pressure is observed, however, and at approximately 14 Kbars the compressibilities on (110), (021) and in the chain direction are all identical ( $\sim 1 \times 10^{-6} \text{ cm}^2/\text{kg}$ ). Thus the anisotropy in lattice compressibility usually assumed for crystalline polymers has essentially disappeared at these pressures for phase II  $\text{PVF}_2$ . The decrease in lattice

compressibility with pressure for phase I is also shown.

Some comment concerning the piezo-electric activity of  $\text{PVF}_2$  is important since this polymer is unique in this respect. If we assume that piezo-electricity arises from lattice compression of dipoles then it should be noted that the lattice compressibility in the dipole direction is important. Phase I  $\text{PVF}_2$  shows the greatest activity and the dipole direction is close to the B-axis direction. The lattice compressibility in the b-direction is calculated to be  $4.2 \times 10^{-6} \text{ cm}^2/\text{kg}$ . The lattice compressibility in the a-direction for phase II is calculated to be  $\sim 11.4 \times 10^{-6} \text{ cm}^2/\text{kg}$ . The piezo-electric activity for phase II  $\text{PVF}_2$  films is less than that observed for phase I films and this is usually attributed to the centrosymmetric lattice for phase II. The compressibility data obtained suggests a very great improvement in piezo-electric activity would be expected if the phase II crystal structure were non-centrosymmetric, since the piezo-electric coefficient should be roughly proportional to lattice compressibility parallel to the dipole direction. In fact, recent reports suggest that a polar phase II structure can be produced by poling films with very high poling voltages<sup>(17)</sup>. Of course, for the case of the phase II crystal structure the dipole direction is no longer perpendicular to the chain axis. Nevertheless, based on the data observed, we conclude that observations of the piezo-electric activity of polar phase II films may be very interesting.



ACKNOWLEDGMENT

The authors gratefully acknowledge the financial support of the Office of Naval Research (Contract N00014-75-C-0540) for these research studies.



## REFERENCES

1. T. Ito and H. Marui, Polym. J. 2 , 768 (1971)
2. H. D. Flack, J. Polymer Sce. A-2 10, 1799 (1972)
3. D. C. Bassett, S. Block and S. J. Piermarini, J. Appl. Phys. 45, 4146, (1974)
4. T. P. Sham, B. A. Newman and K. D. Pae, J. Materials Sci. 12, 771, (1977)
5. K. D. Pae, B. A. Newman and T. P. Sham, J. Materials Sci. 12, 1793, (1977)
6. B. A. Newman, T. P. Sham and K. D. Pae, J. Appl. Physics 48, 4092 (1977)
7. M. Yasuniwa, R. Enoshita, and T. Takemura, Japanese J. Appl. Phys. 15, 1421 (1976)
8. T. Ito, Sen-I Gakkaishi 32, (2), 46, (1976)
9. W. W. Doll and J. B. Lando, J. Macromol, Sci B2, 219, (1968)
10. W. W. Doll and J. B. Lando, J. Macromol Sci. B4, 889, (1970)
11. R. Hasagawa, M. Kokayashi and H. Tadokoro, Polymer J. 3, 591, (1972)
12. R. Hasegawa, Y. Takahashi, Y. Chatani, and H. Tadokoro , Polymer J. 3, 600, (1972)
13. K. Matsushige, K. Nagata and T. Takemura, Japan J. Appl. Phys. Vol 17 No. 3, 467, (1978)
14. B. A. Newman, T. P. Sham and K. D. Pae, J. Materials Sci., 12, 1064, (1977)
15. J. B. Lando, H. G. Olf and A. Peterlin, J. Polymer Sci. A-I 4, 941, (1966)
16. T. Ito, J. Cryst. Soc. Japan, 16, 318 (1974)
17. M. G. Broadhurst, G. T. Davis, J. E. McKinney and R. E. Collins  
Bulletin of the American Physical Society 23, P 369, March 1978

## FIGURE LEGENDS

- Fig. 1 X-ray diffraction pattern of  $\text{PVF}_2$  Phase II at  $\sim 5$  kbars.
- Fig. 2 X-ray diffraction pattern of  $\text{PVF}_2$  phase I at  $\sim 5$  kbars.
- Fig. 3 Comparison of phase II (110) and (021) lattice compressive strains versus pressure with polyethylene (110) planes.
- Fig. 4 Comparison of lattice compressive strains in the chain direction for polyethylene, polytetrafluoroethylene, and  $\text{PVF}_2$  phase II.
- Fig. 5 Phase II lattice parameter variation with pressure
- Fig. 6 Comparison of lattice compressive strains in the chain direction for polyethylene, polytetrafluoroethylene, and  $\text{PVF}_2$  phase I
- Fig. 7 Lattice compressive strain variation with pressure for phase I
- Fig. 8 Comparison of volumetric strain variation with pressure for phase I, phase II and polyethylene.
- Fig. 9 Variation of bulk compressibility with pressure for phase I, Phase II and polyethylene.
- Fig. 10 Linear Compressibilities in phase I and phase II.



